



Title	Characterization of the anisotropic mechanical properties of excised human skin
Authors(s)	Ní Annaidh, Aisling, Bruyère, Karine, Destrade, Michel, Gilchrist, M. D., Otténio, Méline
Publication date	2012-01
Publication information	Ní Annaidh, Aisling, Karine Bruyère, Michel Destrade, M. D. Gilchrist, and Méline Otténio. "Characterization of the Anisotropic Mechanical Properties of Excised Human Skin." Elsevier, January 2012. https://doi.org/10.1016/j.jmbbm.2011.08.016 .
Publisher	Elsevier
Item record/more information	http://hdl.handle.net/10197/4616
Publisher's statement	This is the author's version of a work that was accepted for publication in Journal of the Mechanical Behavior of Biomedical Materials. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Journal of the Mechanical Behavior of Biomedical Materials (5, 1, (2012)) DOI: http://dx.doi.org/10.1016/j.jmbbm.2011.08.016
Publisher's version (DOI)	10.1016/j.jmbbm.2011.08.016

Downloaded 2026-05-02 01:12:29

The UCD community has made this article openly available. Please share how this access benefits you. Your story matters! (@ucd_oa)



© Some rights reserved. For more information

Characterising the Anisotropic Mechanical Properties of Excised Human Skin

A. Ní Annaidh^{a,b}, K. Bruyère^c, M. Destrade^{a,d}, M.D. Gilchrist^{a,e}, M. Otténio^c

^a*School of Mechanical & Materials Engineering, University College Dublin, Belfield, Dublin 4, Ireland*

^b*Institut Jean Le Rond D'Alembert, UMR 7190, CNRS-UPMC, 4 place Jussieu, 75005 Paris, France*

^c*Université de Lyon, F-69622, Lyon, France, Ifsttar, LBMC, UMR_T9406, F-69675, Bron, Université Lyon 1, Villeurbanne*

^d*School of Mathematics, Statistics and Applied Mathematics, National University of Ireland Galway, Galway, Ireland*

^e*School of Human Kinetics, University of Ottawa, Ontario K1N 6N5, Canada*

Abstract

The mechanical properties of skin are important for a number of applications including surgery, dermatology, impact biomechanics and forensic science. In this study we have investigated the influence of location and orientation on the deformation characteristics of 56 samples of excised human skin. Uniaxial tensile tests were carried out at a strain rate of 0.012s^{-1} on skin from the back. Digital Image Correlation was used for 2D strain measurement and a histological examination of the dermis was also performed. The mean ultimate tensile strength (UTS) was $21.6 \pm 8.4\text{MPa}$, the mean failure strain $54 \pm 17\%$, the mean initial slope $1.18 \pm 0.88\text{MPa}$, the mean elastic modulus $83.3 \pm 34.9\text{MPa}$ and the mean strain energy was $3.6 \pm 1.6\text{MJ/m}^3$. A multivariate analysis of variance has shown that these mechanical properties of skin are dependent upon the orientation of Langer lines ($P < 0.0001$ - $P = 0.046$). The location of specimens on the back was also found to have a significant effect on the UTS ($P = 0.0002$), the elastic modulus ($P = 0.001$) and the strain energy ($P = 0.0052$). The histological investigation concluded that there is a definite correlation between the orientation of Langer Lines and the preferred orientation of collagen fibres in the dermis ($P < 0.001$). The data obtained in this study will provide essential information for those wishing to model the skin using a structural constitutive model.

Keywords: Soft tissue, Langer lines, Tensile Properties, Histology

1. Introduction

Skin is a complex multi-layered material which can broadly be divided into two main layers, the epidermis and the dermis. The epidermis consists of cells and cellular debris, and the dermis consists of mostly networks of the fibrous proteins collagen, reticulin and elastin (Wilkes et al., 1973). Collagen fibres account for 75% of the dry weight of dermal tissue (Wilkes et al., 1973) and it is these fibres which are responsible for the strength of the skin.

Skin is a highly non-linear, anisotropic, viscoelastic and nearly incompressible material. A typical stress-stretch graph for skin (see Fig. 3) exhibits non-linear behavior and its response is usually described as three-phase (Brown, 1973). In the initial loading phase, skin is very compliant and large deformation occurs at a relatively low applied load. At this stage the fibres are largely unaligned. In the second phase the stiffness of the skin gradually increases as the fibres align themselves in the direction of applied load. The third phase is an almost linear phase whereby the stiffness increases rapidly as the collagen fibres are mostly aligned and the overall mechanical response becomes dependent upon the mechanical properties of the collagen fibres, which are three grades of magnitude stiffer than elastin.

That skin is anisotropic was recognized as far back as the 19th century by Karl Langer (1861), who mapped the natural lines of tension which occur within the skin. These lines are identified by puncturing the skin with a circular device. The wounds then assume an elliptical shape and by joining the major axes of the ellipses a system of lines can be drawn as shown in Fig. 1(a). These lines are known as the Langer lines. While Langer lines are the best known skin tension lines, many variations on the original lines proposed by Langer have been made. These include the Cox lines (Cox, 1941), Kraissl lines (Kraissl, 1951) and Relaxed Skin Tension Lines (Borges, 1984).

Early tensile tests suggested that the deformation characteristics of skin are dependent upon specimen orientation with respect to the Langer lines (Ridge and Wright, 1966). More recent work conducted using Optical Coherence Elastography in-vivo, indicates a large difference between the Young moduli of skin along directions parallel and orthogonal to the Langer lines (Liang and Boppart, 2010). In this study, we provide new experimental data of in-vitro human skin focusing in particular on the anisotropic properties of the skin. We also quantify the degree of anisotropy of the mechanical properties with respect to their Langer line orientation. Finally, we perform a quantitative histological analysis on the dermis of the test samples to examine a possible correlation between the orientation of Langer lines and the preferred direction of collagen fibres.

While many recent publications on skin report in-vivo experiments (Delalleau et al., 2008; Flynn et al., 2011; Moerman et al., 2009), here we have limited our experiments to in-vitro uniaxial tensile tests. As discussed by Holzapfel, there are a number of issues involved with tensile tests (Holzapfel, 2006): The structural integrity of the samples may be disturbed at the lateral edges; due to the soft nature of the test material it is difficult to insert samples without subjecting them to an axial load; and the composition of the material may vary across its thickness. Despite these shortcomings, it was decided to perform in-vitro tensile tests over in-vivo testing for a number of reasons. First, in-vitro tests provide simple stress-strain relationships that can be modeled and quantified easily, since their boundary conditions are well defined. Second, for the application of this work in a further study into the dynamic rupture of skin, we are also interested in failure and rupture of skin, and in-vitro testing makes it possible to test until failure.

Most in-vitro investigations use human skin substitutes such as pigskin, silicone or polyurethane (McCarthy et al., 2007; Gilchrist et al., 2008; Jor et al., 2011; McCarthy et al., 2010) and in-vitro tests on human skin are particularly rare. Those classical publications which do use human skin often rely on outdated equipment and their results can be difficult to interpret (Cox, 1941; Jansen and Rottier, 1958b). However, the development of accurate constitutive models depends heavily upon their material definitions. This study aims to provide new material data for human skin which can be applied to constitutive models in a number of technical areas such as razor blade manufacture, cosmetics, surgical simulation, forensic pathology and impact biomechanics. Uniaxial tensile tests alone are not sufficient to determine multi-dimensional material models for soft tissues and using a simple non-linear regression analysis to determine constitutive parameters may result in non-unique solutions, ill-conditioned equations and slow convergence rates. Ideally, testing of skin would involve planar biaxial tests with an in-plane shear, and separate through-thickness shear tests. While advanced testing protocols like these are not yet available, simple tension tests remain important because they serve to evaluate the level of anisotropy and to provide data which can later be used as validation for models constructed using more complicated testing methods (Holzapfel and Ogden, 2009). Moreover, model parameters can be provided directly from a histological study of the collagen fibre alignment in the dermis which allows for reasonable determination of material responses (Holzapfel, 2006).

2. Materials & Method

2.1. Specimen Preparation

Tensile tests and preparation were carried out in Ifsttar (Institut français des sciences et technologies des transports, de l'aménagement et des réseaux), France. French law allows human corpses that have been donated to science to be used for research purposes. The ethics committee within Ifsttar approved the use of human biological material. Skin was excised from seven subjects: three male, four female. The average age of the subjects was 89 ± 6 years and none had any related skin diseases. Table 1 provides details on the gender and age of each subject at the time of death along with the number of days that elapsed prior to testing.

Table 1: Information on each test subject. *Number of days elapsed after death prior to testing

Gender	Age (years)	Time Elapsed*	Label
Male	97	9	A
Male	91	3	B
Female	97	2	C
Female	81	3	D
Male	89	3	E
Female	85	4	F
Female	86	4	G

Only the skin from the back of the subject was available for use. This was excised from the body with a scalpel. Each sample of skin was cut into a dogbone shape specimen, according to the ASTM D412 Standard tensile test method for vulcanised rubber, using a custom made die (see Fig. 1). Each specimen then had any underlying adipose tissue carefully removed with a scalpel. The thickness of the skin after removal of adipose tissue was measured using a Vernier Calipers and the mean thickness was 2.56 ± 0.39 mm. It was observed that skin removed from the lumbar area of the back contained more adipose tissue than skin from other areas of the back. The dimensions of the test specimens were measured before and after excision. Specimens were obtained in various orientations, shown in Fig. 1, to correlate the specimens with the direction of Langer lines. Each sample was grouped into one of three categories: parallel, perpendicular, or at 45° to the Langer lines. The skin was stored in moistened paper and refrigerated at

4°C until it was ready to be tested. A total of 56 samples were tested successfully. Although, preconditioning is essential for assessing viscoelastic properties (Lokshin and Lanir, 2009), in this case only hyperelastic properties were considered and viscoelastic properties were ignored. The samples were therefore not pre-conditioned prior to testing.

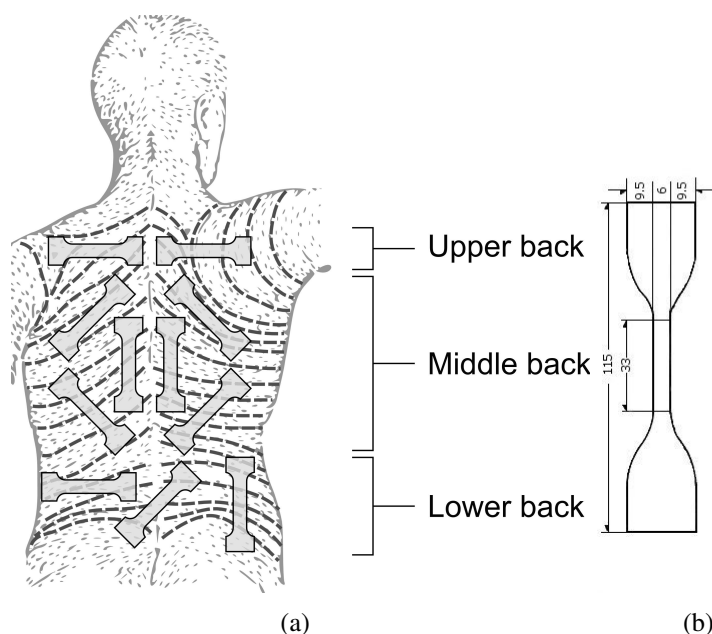


Figure 1: (a) Orientation of samples from the back. Specimens are superimposed onto a map of the Langer lines to indicate their orientation with respect to the lines (Langer, 1861). (b) Dimensions of custom made die (mm)

2.2. Tensile Tests

Tensile tests were performed using a Universal Tensile Test machine. Samples were clamped using specially designed anti-slip clamps, to counteract the tendency of samples to slip in ordinary grips. The velocity of the cross-head was 50mm/min. The tensile load was measured with a 1kN piezoelectric load cell. Each tensile test was videoed with two Dalsa Falcon 1.4M100 digital video cameras at 20 frames/second. This was to record any abnormal behaviour during the experiments and also for the subsequent use of Digital Image Correlation. The gauge length and width were both measured optically. For these tests, the strain

rate was 0.012s^{-1} , nominally the same strain rate as in tests carried out by Jansen and Rottier (1958a).

2.3. Digital Image Correlation

The stretch ratio was calculated via the displacement cell attached to the cross-head of the tensile machine. As validation, the stretch ratio was also calculated via Digital Image Correlation (DIC). DIC is a full-field optical strain measurement technique which uses image registration to measure the 2D or 3D deformation of a material. The technique works by tracking unique features on the surface of the material as it deforms. The correlations were based on images taken with the two Dalsa Falcon video cameras and processed using Vic2D Software (Version 2009-Correlated Solution, Inc.). Black spray paint was applied to the surface of the skin to create the desired random speckled pattern necessary for the correlation.

2.4. Histology

Three biopsies were procured from the test specimens prior to testing. These biopsies were placed in a Formaldehyde solution for fixation for a period exceeding 48 hours. Biopsies were then embedded in paraffin prior to slicing. Each biopsy was sectioned at $5\mu\text{m}$ intervals, creating a number of thin slices which were transferred onto glass slides. Biopsies were sliced in three orthogonal planes as shown in Fig. 2 below. The samples were then stained using a Van Gieson stain, which differentiates collagen fibres by making them appear pink/red. Images were taken of each slide using a Nikon E80i Transmission microscope and CCD camera. The orientation of collagen fibres were then calculated in a fully-automated customized MATLAB routine using the Image Processing Toolbox. The algorithm is described further in (Ní Annaidh et al., 2011).

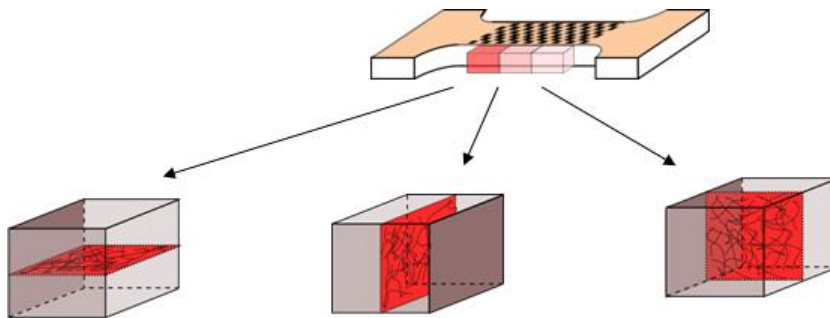


Figure 2: Biopsies of skin samples for purpose of histological staining. Note that the biopsies have been sliced in three orthogonal planes.

2.5. *Statistical Analysis*

A statistical analysis of the experimental results was carried out using the General Linear Model procedure implemented in SAS 9.1 (SAS Institute Inc., USA). A multivariate analysis of variance was utilised, followed by the Tukey-Kramer post-hoc test, to determine the influence of orientation and location of the various test samples. Significance levels for these tests were set to $P < 0.05$. When performing this test a normal distribution was assumed. To ensure our data set followed a normal distribution, a Lilliefors test was performed using the *lillietest* function in MATLAB R2007b.

3. Results

For each tensile test performed a force-displacement curve was obtained. The nominal stress was then calculated by dividing the force by the undeformed cross sectional area of the specimen. The stretch ratio was calculated by dividing the current length of the specimen by the initial length. In this way nominal stress Vs stretch ratio graphs were plotted for each specimen. A number of characteristics from these curves were identified as descriptive parameters. They are illustrated in Fig. 3.

3.1. *Intra-Subject and Inter-Subject Variation*

A difficulty often encountered with the testing of biological tissue is the large variation in experimental results across samples. Fig. 4(a) indicates the intra-subject and inter-subject variation in the UTS between samples. However due to the anisotropic nature of skin this graph is not a true reflection of the repeatability of our results. Fig. 4(b) shows the stress-stretch graphs of ten different samples taken from five subjects. Note that the left and right samples were adjacent to one another but also in the same orientation with respect to the Langer lines. The similarity of these responses between the left and right samples from the same subjects indicates good repeatability of our experiments.

3.2. *Deformation of Specimens After Excision*

It is known that both shrinkage and expansion of specimens can occur upon excision from the body (Cox, 1941; Jansen and Rottier, 1958a; Ridge and Wright, 1966; Lanir and Fung, 1974). This is due to the release of residual stresses within the skin. What remains unclear is the level of residual stress present within the skin and how this may vary with the orientation of specimens. It has been suggested that the shrinkage of excised specimens is greatest in the direction of

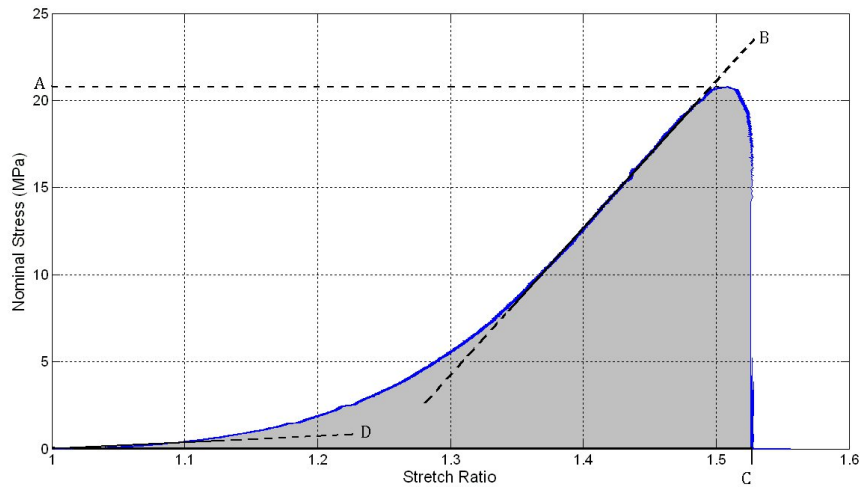


Figure 3: Typical stress-stretch graph for the experiments. The ultimate tensile strength is the maximum stress until failure of the specimen and is indicated by A. The elastic modulus is defined as the slope of the linear portion of the curve shown by B. The failure stretch is the maximum stretch obtained before failure and is shown by C. The initial slope is the slope of the curve at infinitesimal strains and is shown by D. The strain energy is the energy per unit volume consumed by the material during the experiment and is represented by the area under the curve.

Langer lines (Ridge and Wright, 1966) however our results did not corroborate this. Our results showed that 73% of all samples expanded upon excision, while only 27% of all samples shrunk. Of the samples that expanded there was a mean expansion of $5.1 \pm 3.4\%$. Amongst the samples that shrunk, a mean shrinkage of $3 \pm 2.9\%$ was recorded. This is far below the reported maximum figure of 20% shrinkage for human skin (Jansen and Rottier, 1958a) and 40% shrinkage provided for pig skin (Jor et al., 2011). The reason for this discrepancy may be two-fold; firstly, the skin has been excised from the back, not the abdomen, which may be more extensible to accommodate the shrinkage and expansion of the stomach. Secondly, the skin samples were excised from elderly subjects which naturally exhibit less extensibility. This has been previously noted by Jansen and Rottier (1958b) who stated that skin excised from elderly subjects was more likely to expand rather than retract, when compared to younger subjects. Finally, the authors' noted that while shrinkage of the skin may have occurred directly after excision from the body, after subcutaneous fat was removed, the samples often expanded. This poses the question what effect the subcutaneous fat has on the level of shrinkage/expansion in the skin, usually thought to be solely due to the release of residual stresses in the skin.

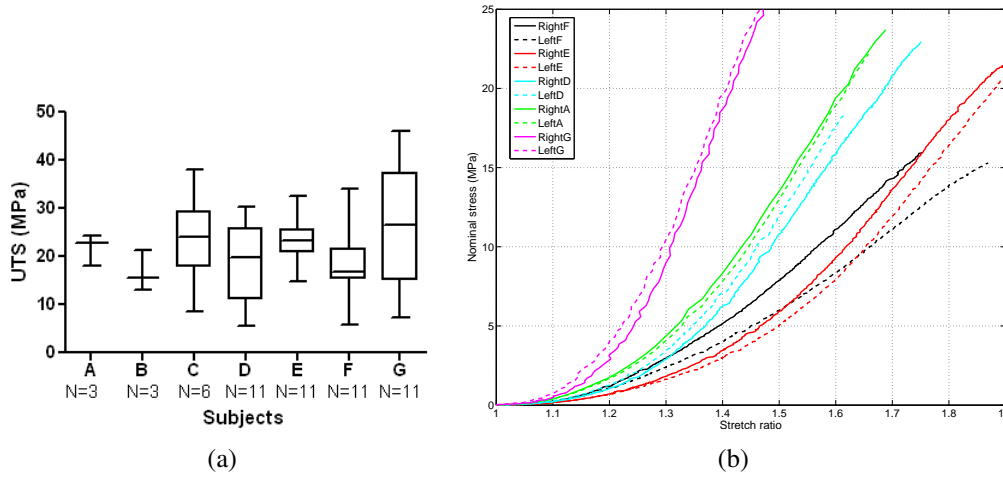


Figure 4: (a) Box and whisker plot of the intra-subject and inter-subject variation in UTS (N=56) for subjects A-G. The whiskers indicate the max and min. The boxes represent the lower and upper quartile and the line is the median. (b) Stress-Stretch response of adjacent samples from the upper back (see Fig. 1) with the same orientation (N=10). Colours indicate different subjects while solid and dashed lines indicate samples to the right and left of the spinal line respectively. This illustrates the inter-subject and intra-subject variation between adjacent samples with the same orientation.

3.3. Histology

The collagen fibres were assumed to form an interweaving lattice structure, as first postulated by Ridge and Wright (1966). Here, the preferred orientation is defined as the mean of the orientations of two families of interweaving fibres. It was assumed that the collagen fibres are distributed according to a transversely isotropic and π -periodic Von Mises distribution. The Von Mises distribution is commonly assumed for directional data. The standard π -periodic Von Mises Distribution is normalized and the resulting distribution is given as follows.

$$\rho(\Theta) = 4\sqrt{\frac{b}{2\pi}} \frac{\exp[b(\cos(2\Theta) + 1)]}{erfi\sqrt{2b}} \quad (1)$$

where Θ is the mean orientation of fibres and b is the concentration parameter associated with the Von Mises distribution. The parameter b was evaluated by the approximation given by Fisher (1993) using the CircStat package available on the MATLAB file exchange (Berens, 2009).

Table 2 shows the calculated concentration parameter b , the mean orientation of collagen fibres and the orientation with respect to Langer lines. A Pearson

correlation test was carried out to test for a correlation between the measured preferred orientation obtained through histology and the perceived orientation of Langer lines. The correlation was deemed to be significant ($P < 0.001$) with a Pearson R value of 0.9487 and an R^2 value of 0.9000.

Table 2: Mean orientation of collagen fibres and their Langer Line orientations. (Note that the data given is axial data i.e. it represents undirected lines and does not distinguish between θ and $\pi + \theta$ (Jones, 2006) e.g. the orientation of 0° and 180° are equivalent).

Orientation with respect to Langer Lines	Preferred Orientation, Θ	Level of dispersion, b
0°	40°	0.5222
0°	163°	1.1605
0°	16°	1.1471
0°	168°	0.6004
45°	40°	0.8388
45°	61°	0.7926
45°	46°	0.7453
45°	53°	0.4209
45°	57°	0.8326
45°	83°	0.9330
90°	73°	0.9007
90°	120°	0.6197

3.4. Influence of Orientation

Specimens were analysed by considering their orientation with respect to the Langer lines (parallel, perpendicular or at 45° to the Langer lines, see Fig. 1). A multiway analysis of variance found the orientation of Langer lines to have a significant effect on the UTS ($P < 0.0001$), the strain energy ($P = 0.0101$), the elastic modulus ($P = 0.0002$), the initial slope ($P = 0.0375$), and the failure stretch ($P = 0.046$). The interaction between orientation and location was also tested i.e., whether the effect of orientation was dependent upon location. This interaction between orientation and location was found to be significant only for the failure stretch ($P = 0.0118$). Fig. 5 and Table 3 display the variation in the mechanical properties between samples of different orientations. The variations are substantial, except for the failure stretch, where the effect of the orientation is complicated by the existence of the interaction between orientation and location.

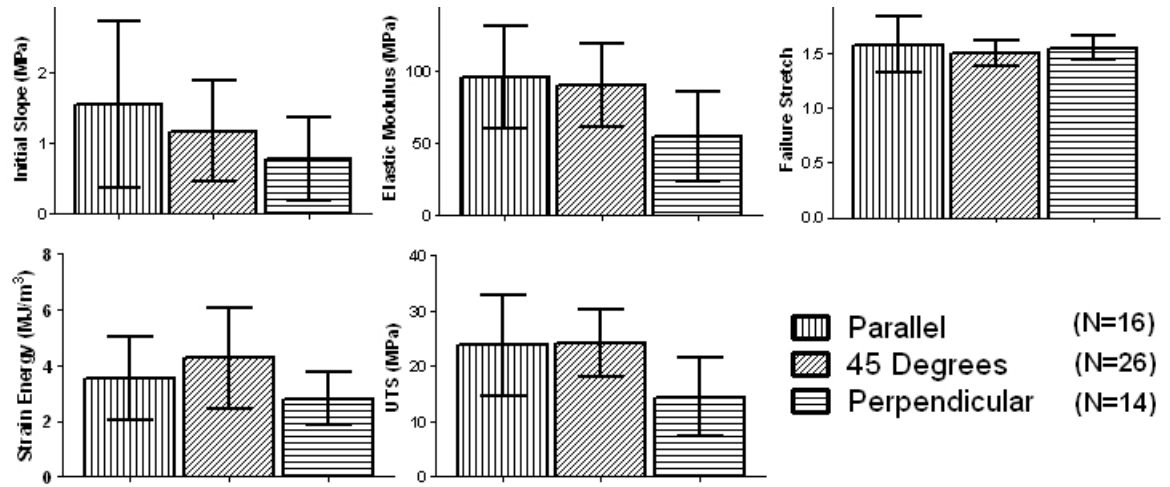


Figure 5: Influence of orientation on the initial slope, elastic modulus, failure stretch, strain energy and UTS. Values given include mean and standard deviations

Table 3: Mean \pm standard deviation for each orientation/location group.

Langer Line Orientation	Location	N	UTS (MPa)	Strain Energy (MJ/m ³)	Failure Stretch	Elastic Modulus (MPa)	Initial Slope (MPa)
Parallel	Middle	9	28.64 ± 9.03	4.28 ± 1.49	1.46 ± 0.07	112.47 ± 36.49	1.21 ± 0.97
Parallel	Bottom	7	17.60 ± 4.77	2.54 ± 0.76	1.74 ± 0.32	73.81 ± 19.41	1.95 ± 1.34
45°	Top	12	22.7 ± 3.61	3.80 ± 0.92	1.52 ± 0.10	82.62 ± 17.36	0.99 ± 0.51
45°	Middle	9	28.85 ± 7.87	5.38 ± 2.59	1.52 ± 0.15	103.49 ± 41.20	1.33 ± 0.96
45°	Bottom	5	20.23 ± 4.18	3.31 ± 0.67	1.43 ± 0.04	82.81 ± 18.43	1.30 ± 0.60
Perpendicular	Middle	9	16.53 ± 5.71	2.98 ± 0.89	1.52 ± 0.08	63.75 ± 24.59	0.91 ± 0.68
Perpendicular	Bottom	5	10.56 ± 8.41	2.44 ± 1.04	1.61 ± 0.14	37.66 ± 36.41	0.54 ± 0.33

3.5. Influence of Location

When results were grouped into three locations (Upper Back, Middle Back and Lower Back, see Fig. 1), a multiway analysis of variance also found the lo-

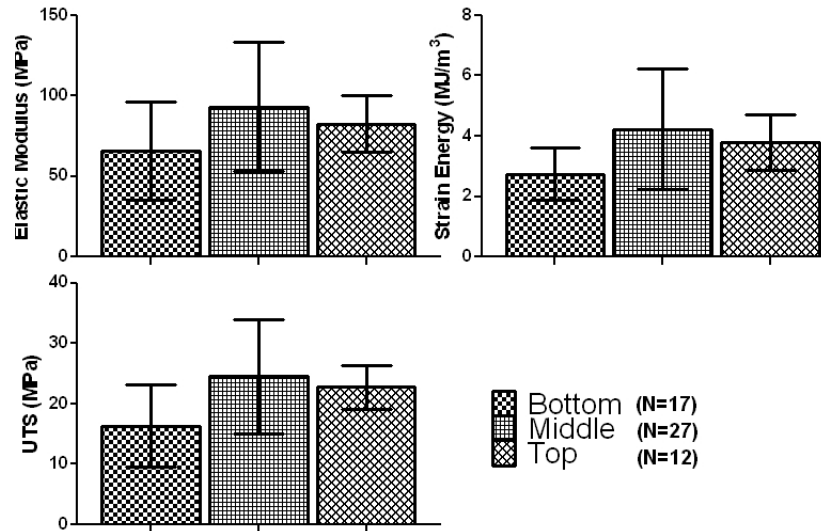


Figure 6: Influence of location on back on the elastic modulus, strain energy and UTS. Values given include mean and standard deviations.

cation of specimens to have a significant effect on the UTS ($P=0.0002$), the strain energy ($P=0.0052$) and the Elastic Modulus ($P=0.001$), but neither on the failure stretch nor the initial slope. Fig. 6 displays variations in the mechanical properties between different locations on the back for the three properties which showed a significant effect i.e., the elastic modulus, UTS and strain energy. Note that there was no significant effect noted for either the initial slope or the failure stretch.

3.6. Digital Image Correlation

An important feature of DIC is its ability to calculate local strains throughout the plane of the test specimens. Fig. 7(a) shows a comparison between the local stretch values, obtained through DIC, and the overall stretch values, obtained from the displacement sensor (DS), throughout the duration of a test. It can be seen that there is good agreement for most of the duration of the test. However, upon closer inspection it was found that a local magnification of the stretch ratio occurred just before rupture, close to the rupture site (for magnitudes, see Table 4). Fig. 7(b) shows the distribution of strains throughout the sample for a frame just before rupture. For some samples this magnification was very localised while for others it was distributed over a larger area. A similar result was reported by Jacquemoud et al. (2007) who found that at the rupture site, the local strain values can be up to

twice as large as what is measured using overall specimen strains calculated over the entire length of a specimen.

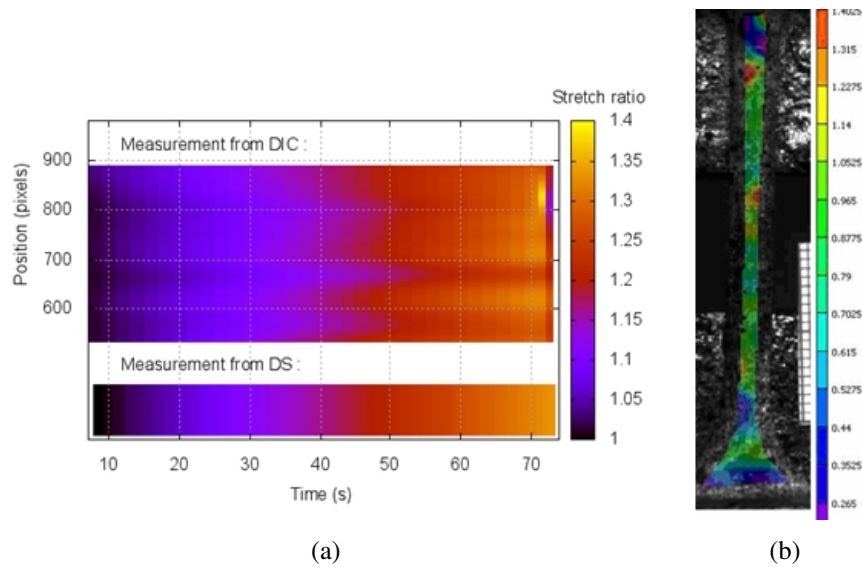


Figure 7: (a) Comparison of stretch measurement from DIC and DS over the length of the specimen throughout the duration of a given tensile test. (b) Distribution of local Lagrangian strains just before rupture. Note the area of localised magnification in red. This is the location where rupture subsequently occurred.

Table 4: Local and overall maximum stretch ratios for five different samples. Local magnification of the stretch ratio occurs just before rupture.

Sample	Local Max Stretch Ratio	Overall Specimen Stretch Ratio
1	1.47	1.38
2	1.45	1.40
3	1.65	1.45
4	1.70	1.48
5	1.70	1.50

4. Discussion

When comparing our own data to that in the literature it can be seen that there is much variation between authors. This is to be expected for biological tissues.

First, because of the biological variability between subjects; second, because of the anisotropic nature of skin itself; and third, because of the sensitivity of biological tissues to test conditions. Table 5 compares results obtained from the literature to our own results. The mean ultimate tensile strength was 21.6 ± 8.4 MPa, the mean failure strain $54 \pm 17\%$, the mean initial slope 1.18 ± 0.88 MPa, the mean elastic modulus 83.3 ± 34.9 MPa and the mean strain energy was 3.6 ± 1.6 MJ/m³. It can be seen that our experimental results fall within the ranges found in the literature.

Table 5: Comparison of results obtained to results in the literature. All experiments were carried out in-vitro on excised human skin. Results are displayed as means (\pm standard deviation) and ranges.

Author	UTS (MPa)	Failure Strain %	Elastic Modulus MPa	Initial Slope MPa	Location*	Age
Jansen et al.	1-24	17-207	2.9-54.0	0.69-3.7	Ab	0-99
Daly			30	0.005	Ab	
Silver	2-15		18.8	0.1	Ab & T	47-86
Ridge et al.	15	30			Ab & A	0-90
Stark		16-52	0.26-0.83		V	15-30
Vogel	5-32	30-115	15-150			0-90
Jacquemoud	5.7-12.6	27-59	19.5-87.1		F & A	62-98
Our results	21.6 ± 8.4	54 ± 17	83.3 ± 34.9	1.18 ± 0.88	Back	81-97

*Ab = abdomen, T = thorax, V = various, F = forehead, A = arm

It has been well documented over the years that the deformation characteristics of skin are dependent upon specimen orientation, but few authors describe the level of anisotropy involved in much detail. In this study, we have provided statistical information on the effect of Langer line orientation on the UTS, strain energy, failure strain, initial slope, and elastic modulus. We have been unable to establish a link between the level of shrinkage of skin upon excision and the orientation of the Langer lines. Instead we found that the majority of samples actually expanded upon excision. The reason for this may be because the skin has been excised from the back and not the abdomen or it may be because the tissue samples were from elderly subjects which are known to exhibit less extensibility. This has been previously noted by Jansen and Rottier (1958a,b) who stated that skin excised from elderly subjects was more likely to expand rather than retract, when compared to younger subjects.

Previous studies show that the properties of skin are dependent upon specimen location (Haut, 1989; Sugihara et al., 1991). Our results also indicate that the UTS, strain energy and elastic modulus vary depending on location. However, as only skin from the back was available for testing, the location of specimens could only be categorised into upper back, middle back and lower back regions. It was nonetheless advantageous to gain information on skin from the back because it is seldom as readily available as that from the abdominal area.

All subjects were between the ages of 81 and 97. This meant that no comparisons based on the age of subjects could be performed. Numerous other studies have investigated the influence of age on the mechanical properties of skin and it has been well documented that the extensibility of skin decreases with age (Vogel, 1987; Haut, 1989; Sugihara et al., 1991). Furthermore, a number of days had elapsed between the time of death and testing (see Table 1) but it has been previously demonstrated that skin samples can be refrigerated for up to 48 hours under the right conditions with no discernible effects on the mechanical properties (Daly, 1982) and for up to 21 days for thoracic aortas under certain conditions (Adham et al., 1996).

DIC is a common strain measurement technique in biomechanics, however until now it has been used mostly for in-vivo experiments or at low strains (Moerman et al., 2009). The results yielded from the present use of DIC may be useful in the future as validation for a finite element approach. Also the reported local maximum strain values are of interest to those wishing to model failure of biological tissues.

In this paper, our data has been examined with respect to the perceived orientation of Langer lines. However, the Langer lines are known to vary with location, age and gender and no universal pattern of maximum tensions exist (Brown, 1973). The orientation of the Langer lines cannot be identified with certainty unless the skin of a whole cadaver is punctured, an option which was not feasible for this study. Given the importance of the Langer lines on the mechanical properties of skin there is a need for patient-specific maps to be established in-vivo and in real time. These could be produced by relying on sophisticated imaging techniques such as those produced by ultrasonic surface wave propagation or optical coherence tomography and may eventually have applications in cosmetic surgery.

Cox (1941) and Stark (1977) both illustrated that the orientations of Langer lines remain even after the skin is removed from the body and the skin tension released, and concluded that the lines have an anatomical basis. However it remains unclear in the literature whether the Langer lines have a structural basis, and to the authors' knowledge there is no quantitative data published on this point. By

identifying the orientation of collagen fibres in the dermis we have shown that there is a correlation between their orientation and that of the Langer Lines. However, it is only when a quantitative study is performed that this becomes apparent. Knowledge of the collagen fibre orientation along with the presented stress-strain data will also facilitate the determination of material parameters for structurally based constitutive models for skin.

Acknowledgments

This research was supported by a Marie Curie Intra European Fellowship within the 7th European Community Framework Programme, awarded to MD. It was also supported by IRCSET (Irish Research Council for Science, Engineering and Technology) through the Ulysses Award, and IRCSET and the Office of the State Pathologist (Irish Department of Justice and Law Reform) through the EMBARK scholarship awarded to ANíA. This work is supported by grants from Ile-de-France.

Adham, M., Gournier, J.-P., Favre, J.-P., De La Roche, E., Ducerf, C., Baulieux, J., Barral, X., Pouyet, M., 1996. Mechanical characteristics of fresh and frozen human descending thoracic aorta. *Journal of Surgical Research* 64 (1), 32–34.

Berens, P., 2009. Circstat: A MATLAB toolbox for circular statistics. *Journal of Statistical Software* 31 (10).

Borges, A., 1984. Relaxed skin tension lines (RSTL) versus other skin lines. *Plastic Reconstructive Surgery* 73 (1), 144–150.

Brown, I. A., 1973. A scanning electron microscope study of the effects of uniaxial tension on human skin. *British Journal of Dermatology* 89 (383-393).

Cox, H., 1941. The cleavage lines of the skin. *British Journal of Surgery* 29 (114), 234–240.

Daly, C. H., 1982. Biomechanical properties of dermis. *Journal of Investigative Dermatology* 79, 17–20.

Delalleau, A., Josse, G., Lagarde, J. M., Zahouani, H., Bergheau, J. M., 2008. Characterization of the mechanical properties of skin by inverse analysis combined with an extensometry test. *Wear* 264 (5-6), 405–410.

- Fisher, N., 1993. *Statistical Analysis of Circular Data*. Cambridge University Press, Cambridge.
- Flynn, C., Taberner, A., Nielsen, P., 2011. Mechanical characterisation of in vivo human skin using a 3d force-sensitive micro-robot and finite element analysis. *Biomechanics and Modeling in Mechanobiology* 10, 27–38.
- Gilchrist, M. D., Keenan, S., Curtis, M., Cassidy, M., Byrne, G., Destrade, M., 2008. Measuring knife stab penetration into skin simulant using a novel biaxial tension device. *Forensic Science International* 177 (1), 52–65.
- Haut, R. C., 1989. The effects of orientation and location on the strength of dorsal rat skin in high and low speed tensile failure experiments. *Journal of Biomechanical Engineering* 111 (2), 136–140.
- Holzapfel, G. A., 2006. Determination of material models for arterial walls from uniaxial extension tests and histological structure. *Journal of Theoretical Biology* 238 (2), 290 – 302.
- Holzapfel, G. A., Ogden, R. W., 2009. On planar biaxial tests for anisotropic nonlinearly elastic solids. a continuum mechanical framework. *Mathematics and Mechanics of Solids* 14 (5), 474–489.
- Jacquemoud, C., Bruyere-Garnier, K., Coret, M., 2007. Methodology to determine failure characteristics of planar soft tissues using a dynamic tensile test. *Journal of Biomechanics* 40 (2), 468–475.
- Jansen, L., Rottier, P., 1958a. Comparison of the mechanical properties of strips of human abdominal skin excised from below and from above the umbilic. *Dermatologica* 117, 252–258.
- Jansen, L., Rottier, P., 1958b. Some mechanical properties of human abdominal skin measured on excised strips. *Dermatologica* 117, 65–83.
- Jones, T. A., 2006. Matlab functions to analyze directional (azimuthal) data—I: Single-sample inference. *Computers & Geosciences* 32 (2), 166–175.
- Jor, J. W. Y., Nielsen, P. M. F., Nash, M. P., Hunter, P. J., 2011. Modelling collagen fibre orientation in porcine skin based upon confocal laser scanning microscopy. *Skin Research and Technology*.

- Kraissl, C., 1951. The selection of appropriate lines for elective surgical incisions. *Plastic and Reconstructive Surgery* 8 (1), 1–28.
- Langer, K., 1861. On the anatomy and physiology of the skin. The Imperial Academy of Science, Vienna. Reprinted in (1978): *British Journal of Plastic Surgery* 17 (31), 93–106.
- Lanir, Y., Fung, Y. C., 1974. Two-dimensional mechanical properties of rabbit skin–ii. experimental results. *Journal of Biomechanics* 7 (2), 171–174.
- Liang, X., Boppart, S. A., 2010. Biomechanical properties of in vivo human skin from dynamic optical coherence elastography. *IEEE Transactions on Biomedical Engineering* 57 (4), 953–959.
- Lokshin, O., Lanir, Y., 2009. Viscoelasticity and preconditioning of rat skin under uniaxial stretch: Microstructural constitutive characterization. *Journal of Biomechanical Engineering* 131 (3).
- McCarthy, C. T., Hussey, M., Gilchrist, M. D., 2007. On the sharpness of straight edge blades in cutting soft solids: Part I - Indentation experiments. *Engineering Fracture Mechanics* 74 (14), 2205–2224.
- McCarthy, C. T., Ní Annaidh, A., Gilchrist, M. D., 2010. On the sharpness of straight edge blades in cutting soft solids: Part II - Analysis of blade geometry. *Engineering Fracture Mechanics* 77 (3), 437–451.
- Moerman, K. M., Holt, C. A., Evans, S. L., Simms, C. K., 2009. Digital image correlation and finite element modelling as a method to determine mechanical properties of human soft tissue in vivo. *Journal of Biomechanics* 42 (8), 1150–1153.
- Ní Annaidh, A., Bruyère, K., Destrade, M., Gilchrist, M., Maurini, C., Otténio, M., Saccomandi, G., 2011. Automated estimation of collagen fibre dispersion in the dermis and its contribution to the anisotropic behaviour of skin. In *Preparation*.
- Ridge, M., Wright, V., 1966. The directional effects of skin. A bio-engineering study of skin with particular reference to Langer's lines. *Journal of Investigative Dermatology* 46 (4), 341–346.

- Silver, F. H., Freeman, J. W., DeVore, D., 2001. Viscoelastic properties of human skin and processed dermis. *Skin Research and Technology* 7 (1), 18–23.
- Stark, H. L., 1977. Directional variations in the extensibility of human skin. *British Journal of Plastic Surgery* 30 (2), 105–114.
- Sugihara, T., Ohura, T., Homma, K., Igawa, H., 1991. The extensibility in human skin: variation according to age and site. *British Journal of Plastic Surgery* 44, 418–422.
- Vogel, H., 1987. Age dependence of mechanical and biochemical properties of human skin. *Bioengineering and the skin* 3, 67–91.
- Wilkes, G., Brown, I., Wildnauer, R., 1973. The biomechanical properties of skin. *CRC Critical Reviews in Bioengineering* 1 (4), 453–495.