



Title	Experimental characterisation of Polyethylene Terephthalate (PET) bottle Eco-bricks
Authors(s)	Taaffe, Jonathan, O'Sullivan, Seán, Rahman, Muhammad Ekhlaur, Pakrashi, Vikram
Publication date	2014-08
Publication information	Taaffe, Jonathan, Seán O'Sullivan, Muhammad Ekhlaur Rahman, and Vikram Pakrashi. "Experimental Characterisation of Polyethylene Terephthalate (PET) Bottle Eco-Bricks." Elsevier, August 2014. https://doi.org/10.1016/j.matdes.2014.03.045 .
Publisher	Elsevier
Item record/more information	http://hdl.handle.net/10197/10416
Publisher's statement	This is the author's version of a work that was accepted for publication in Materials & Design. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Materials & Design (60 (2014)) https://doi.org/10.1016/j.matdes.2014.03.045
Publisher's version (DOI)	10.1016/j.matdes.2014.03.045

Downloaded 2026-05-02 00:25:14

The UCD community has made this article openly available. Please share how this access benefits you. Your story matters! (@ucd_oa)



© Some rights reserved. For more information

1 **Experimental Characterisation of Polyethylene Terephthalate**
2 **(PET) Bottle Eco-Bricks**

3 Jonathan Taaffe¹, Seán O’Sullivan¹, Muhammad Ekhlalur Rahman² and Vikram
4 Pakrashi^{1*}

5

6 ¹Dynamical Systems and Risk Laboratory, Civil and Environmental Engineering, School
7 of Engineering, University College Cork, Ireland

8 ²School of Engineering & Science, Curtin University Sarawak, Malaysia

9

10 **Corresponding Author:** Dr. Vikram Pakrashi, Lecturer in Structural Engineering,
11 Department of Civil and Environmental Engineering, University College Cork, Ireland.

12 Phone: +353(0)214903862 Email: V.Pakrashi@ucc.ie Fax: +353(0)214276648

13

14

15

16

17

18

19

20

21

22

23

24

25

1 **Abstract**

2 This paper addresses the issue of recycling waste plastic by considering the feasibility of
3 use of Eco-bricks for constructional purposes. The Eco-bricks are formed by packing
4 plastic within Polyethylene Terephthalate (PET) bottles. Guidelines were provided for the
5 construction of Eco-bricks. Experiments were carried out to characterise some of the
6 properties of these bricks. Compression test, sound insulation assessment and light
7 transmission were considered in this regard and compared with traditional construction
8 materials and conditions. Possible applications of Eco-bricks were discussed. The paper
9 presents the first attempt to characterise these bricks and the results encourage future use
10 of them to a significantly wider extent and for various purposes.

11

12 Keywords: Plastic waste, Compressive Test, Sound Insulation, Light Transmission, Eco-
13 brick

14

15 **1. Introduction**

16 Waste management problems related to high production of plastic is an extremely
17 important global challenge [1-4] and recycling or recovery [5] routes of plastic solid
18 waste have been highlighted by a number of researchers [6]. The mineralisation rate
19 from long-term biodegradation experiments of both Ultra-Violet (UV)-irradiated samples,
20 non-pre-treated, and additive-free low density polyethylene samples, in natural soils
21 indicate it is likely to take more than 100 years [7]. In the last 20 years both diminishing
22 landfill capacity and concern of general environmental issues have resulted in the United

1 States and the European Union (EU) introducing new legislations to promote waste
2 reduction [2, 9]. The impact of plastics on primary and secondary carbon footprint is also
3 a very important factor that has been highlighted by researchers [3]. High Density
4 Polyethylene (HDPE), Low Density Polyethylene (LDPE) and Linear Low Density
5 Polyethylene (LLDPE) are widely used for the manufacture of plastic bags [10].
6 Supermarkets shopping bags, the most prevalent type of plastic bag, are ideally produced
7 out of LLDPE to obtain the desired thickness and glossy finish. LDPE is usually used if
8 the producer is looking for a very thin and gauzy bag [11]. Life Cycle Analysis can
9 provide important insights to the effects of such plastic products [12-14]. Consumer
10 behaviour and governmental policies have an important role in the disposal stage. For
11 example in Ireland a plastic bag levy was first introduced on 4th March 2002 at the rate
12 of 15 cent per disposable plastic bag. It had an immediate effect on consumer behaviour
13 with a decrease in plastic bag usage from an estimated 328 bags per capita to 21 bags per
14 capita overnight. The current levy of 22 cent was introduced on 1 July, 2007. It was
15 increased as the bags per capita had increased to 31 during 2006. The aim of the increase
16 is to reduce the plastic bag per capita usage to 21 or lower [15]. This number may be
17 compared to the equivalents in China and India as 1095 and 150 respectively [3].

18 Re-use of plastic bottles have been considered for the construction industry and there
19 exists studies on concrete [16], on mortars containing Polyethylene Terephthalate (PET)
20 waste aggregates [17], use of rice husk and plastics [18], application as a composite in
21 concrete [19], aggregate replacement in concrete [20-22], investigation in water-cement
22 ratios of such concrete with PET bottles [23] and even as soil reinforcement [24].

1 Although significant work is present in the use of plastic bottles as additive to traditional
2 construction materials, there exists a significant gap in studying if the bottles themselves
3 can be used for potential applications in construction and very little study exists
4 attempting to characterize such solutions to any extent. Recently POLLI-Bricks have
5 considered the usage of plastic bricks [25]. There are some examples, especially in Latin
6 American countries where a concept similar to eco-brick has been used as a part of a
7 volunteering campaign and for detailing eco-parks or certain structural features.

8 This paper presents a first characterization study on eco-bricks, which are essentially
9 empty PET beverage bottles filled with waste plastic bags or other discarded plastic.
10 Manufacturing aspects, consistency in weight and mechanical strength aspects are
11 investigated as well as noise insulation and light insulation aspects. Experimental
12 investigation is carried out on eco-bricks this regard and potential applications are
13 discussed.

14

15

16 **2. Background to Characterisation**

17 **2.1 Compressive Strength**

18 Compressive strength is a typical value quoted for units of construction but may have
19 different interpretations based on the brittleness, ductility and the load-displacement
20 characteristics of a material. Independent of a true failure or rupture of the material, a
21 yield in compression is always representative of a characteristic strength of a unit of
22 construction. Uncertainties in production within or between batches are acknowledged in
23 construction design, but within batch variations are expected to be relatively lower for a

1 manufacturing unit under appropriate control. However, it is difficult to assess such
2 uncertainties with confidence for small and medium sized jobs by observing the number
3 of defectives in a batch.

4

5 **2.2 Sound Insulation**

6 In building acoustics, the main frequency range used to assess sound insulation lays
7 between the 100 and 3150 Hz one-third-octave-bands and an optional extended frequency
8 range is defined between the 50 and 5000 Hz one-third-octave-bands. The range between
9 50 and 5000 Hz is referred to as the building acoustics frequency range. It is possible to
10 define frequency ranges using one-third-octave-band centre frequencies low frequency
11 range (50–200 Hz), mid-frequency range (250–1000 Hz) and high-frequency range
12 (1250–5000 Hz) [26]. For this paper it is assumed that ‘typical rooms’ have volumes
13 between 20 and 200 m³ and this covers the majority of practical situations. Measurements
14 of sound insulation may be laboratory measurements that provide information at the
15 design stage, field measurements that demonstrate whether the required sound insulation
16 has been achieved in a building, and field measurements that help an engineer solve
17 sound insulation problems in existing buildings. For many buildings the acoustic
18 requirements are described in building regulations; hence repeatability, reproducibility,
19 and relevance (i.e. the link between the measured sound insulation and the satisfaction of
20 the building occupants) are particularly important for airborne and impact sound
21 insulation. Laboratory measurements of the acoustic properties of materials and building
22 elements (e.g. walls, floors, windows, doors) are primarily used for comparing products
23 and calculating the sound insulation in situ. Measurements of material properties are

1 particularly useful in assessing whether one material in the construction could be
2 substituted for a different one, and for use in prediction models. Testing may also be
3 carried out in-situ with limited number of samples. Sound insulation is heavily dependent
4 on the quality of construction and workmanship. The test room should ideally be empty
5 and unfurnished. It is common to express sound intensity on a logarithmic scale, called
6 decibel SPL (Sound Power Level). On this scale, 0 dB SPL is a sound wave power of 10-
7 16 watts/cm², roughly the weakest sound detectable by the human ear. Normal speech is
8 at around 60 dB SPL, while painful damage to the ear occurs at around 140 dB SPL [27].

9

10 **2.3 Light Transmission**

11 Transmission is the property of a substance to permit the passage of light, with some or
12 none of the incident light being absorbed in the process. If some light is absorbed by the
13 substance, then the transmitted light will be a combination of the wavelengths of the light
14 that was transmitted and not absorbed [28]. The transmission coefficient is a measure of
15 how much light (electromagnetic wave) passes through an optical element or a surface.
16 Transmission coefficients can be calculated for either the intensity of the wave or the
17 amplitude. Different instruments are required to assess light transmission. A spectrometer
18 is an instrument used to measure properties of light over a specific portion of the
19 electromagnetic spectrum. The variable measured is most often the intensity of light. The
20 independent variable is usually the wavelength of the light or a unit directly proportional
21 to the photon energy, such as wave number or electron volts, which has a reciprocal
22 relationship to wavelength. An amplified photomultiplier tube (PMT) is designed for
23 detection of light signals from DC to typically 20 kHz. The light to voltage conversion

1 can be estimated by factoring the wavelength-dependent responsivity of the PMT with
2 the transimpedance gain.

3

4 **3. Manufacture and Control of Specimens**

5 Eco-bricks are formed by compacting waste plastic bags within pet bottles. An example
6 of such bottles is presented in Figure 1. The manufacture and control of the various
7 specimens are presented next.

8

9 **3.1 Manufacturing of Specimens**

10 ***3.1.1. Selection of Bottle Size***

11 There are many alternative sizes of plastic bottle to choose from including 500ml, 750ml,
12 1l, 1.25l and 2l bottles. The most appropriate bottle to use was found to be of size 500ml.
13 There are a number of reasons behind this choice. It is quite difficult to manually pack a
14 bottle of larger size. The force required from the stick to compact the plastic into bigger
15 bottles is difficult to reach when packing the bottle by hand. Also, generally larger bottles
16 can come in a variety of sizes due to their larger volume to manipulate the shape of the
17 bottle. Using the 500ml bottle ensures that the geometry of the bottles are usually
18 consistent.

19 ***3.1.2. Packing Material***

20 It is preferred that the waste that goes in as a packing material is of a plastic form. There
21 are some suggestions of using any household waste but most non-plastic household waste
22 do not have as long a decomposition rate as plastic. The decomposition of any material
23 can alter the compaction of the waste within the bottle and as a result compromise the

1 structural integrity of the brick. Any forms of plastic can be used including cling film and
2 food wrapper. The plastic that enters the bottle has to be relatively clean and always dry.
3 This is important because particles of food can cause mould and other unpredictable
4 bacteria to form. However, the majority of food packaging/garbage just needs a quick
5 shake to remove most of the food from the garbage. It is important that the bottle is dried
6 out before the packing process begins.

7 8 **3.1.3. Tapping Test**

9 From experiences of making Eco-bricks it is advised to keep a set number of taps to
10 compress the plastic into the bottle, needing between 4-6 taps for every piece of plastic.
11 At the beginning of manufacturing a brick it takes less effort to compress the plastic but
12 as more is entered it can be noted that the waste needs more force to compress the waste.
13 The 4-6 taps is only a guideline as when one begins the process they will notice that
14 sometimes more taps will be needed to compress the plastic properly as indicated in the
15 next subsections.

16 17 **3.1.4. The Packing Process**

18 Before the packing process begins it is vital to ensure that a proper 'stick' is used to pack
19 with. It must be able to reach the bottom of the bottle and be able to avoid the possibility
20 of breaking. It must also be of a diameter which will fit into the bottle and have the
21 leverage to reach the inner edges of the bottle. It is required that the stick is of sufficient
22 length to ensure that one can have a firm grip on the stick so that it reaches the bottom of
23 the bottle. Considering the alternative lengths of 500ml bottles available the

1 recommendation is a metal rod of diameter 12-16mm and 350-500mm length. A wooden
2 stick could also be used, but the weight of the metal reduces the physical effort needed in
3 packing the garbage. This increases the force applied into the bottle hence increasing the
4 ease of creation. The best method is to start packing the waste in little by little and
5 alternating between adding the plastic and compacting it with the stick. While
6 compacting with the stick the bottle needs to be rotated while pressing down to ensure
7 that the waste will be evenly compacted throughout the bottle. This helps ensure that the
8 bottle will not have any voids and will have the solid properties similar to a concrete
9 block.

10

11 **3.2. Control of Specimen**

12 There are a number of aspects to the manufacturing to the brick that need to be kept to a
13 high standard as one makes the bricks.

14

15 **3.2.1. Manual Checks**

16 From the experience of making Eco-bricks, it is advised that the bottle eco brick should
17 weigh no less than 220g after the packing process. If it is less that this weight it implies
18 that the compression ratio of the brick is insufficient to be considered for structural
19 purposes. The mass per unit volume plays an important role in the strength of Eco-bricks.
20 The relationship is investigated in the next section experimentally. A weight below 220g
21 is acceptable for use as an insulator but lower than this indicates that it might not be
22 strong enough to withstand large pressures. Significant qualitative information can be
23 retrieved about the specimen after construction by touch. When the brick is manufactured

1 if a person can feel the surface area of the bottle to ensure there is not any major voids in
2 the packing. Due to human error in the manufacturing it has been acknowledged in tests
3 that there can be small gaps in the packing but as long as they are not featuring frequently
4 throughout the bottle and that they are so large that they are pose a risk to the structural
5 integrity of the bottle.

6

7 **3.2.2. Void Detection**

8 There are many different options that exist for finding and quantifying voids within the
9 bottle eco brick. These include sophisticated methods like elastic and electromagnetic
10 wave propagation [29]. With knowledge of sound wave propagation and the use of
11 appropriate reference standards along with generally accepted test procedures, a trained
12 operator can identify specific patterns corresponding to the echo response from good
13 parts and from representative flaws. The echo pattern from a test piece may then be
14 compared to the patterns from these calibration standards to determine its condition [30].

15

16 **3.2.3. Sample Checks**

17 It is acknowledged that sampling checks are required when the bricks are manufactured
18 in large quantities. As a guideline, the check for concretes in site may be referred to. As
19 an initial recommendation, one in every ten bricks made by an experienced manufacturer
20 could be tested, as testing every single brick would be very costly and time consuming.

21 Figure 2 presents a flowchart related to the making of Eco-bricks.

22

23

1 **4. Experimental Considerations**

2 **4.1 Compression Test**

3 A Denison compressive testing machine was used for compression test. An extra platen
4 had to be added to the machine to allow for the smaller specimens in the test as 150 x 150
5 x 150 cubes would be the norm for concrete cubes. The brick is first placed into the
6 centre of the machine, with the bottle cap facing away from the front in case the pressure
7 build up forced it to pop off. The initially preload is 5 kN. The full load is applied till
8 there is a sudden drop in force, which results in the machine stopping. The failure is not
9 complete since the specimen is substantially deformed but that no fracture occurs.

10

11 **4.2 Sound Insulation Assessment**

12 It is not possible to test the sound insulation of the bottle “eco-brick” unless an entire
13 room is made out of it. Therefore, to assess the sound insulation of the brick a viable
14 option was to calculate the sound reduction index of the bottle “eco-brick” and undertake
15 a comparable analysis to other bricks used in construction. Sound Reduction Index (R) is
16 a quantity, measured in a laboratory which characterises the sound insulating properties
17 of a material or building element in a stated frequency band [31]. It is possible to
18 estimate the sound reduction index of a solid construction such as a brick wall by using
19 the Mass Law, and this can be used to estimate the sound reduction index of a brick if the
20 mass per unit area is known. To obtain the mass per unit area of the brick, a bottle was
21 split in half with a saw. The half bottle is placed onto a piece of paper, and the outline is
22 traced. The bottle is split up into very small trapezoids and the area of each trapezoid is
23 calculated. Figure 3 presents the method of this conversion for different sections.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23

4.3 Light Transmission Assessment

An amplified photomultiplier tube is used. A buffered output device drives a 50Ω impedance to 5V. The PMM01 housing includes SM1 (1.0352 x 40) threads that are compatible with any number of Thorlabs' SM1-threaded accessories. The housing also includes tapped holes that are compatible with Thorlabs' 30mm cage system.

The PMM01 has three 8-32 (M4 on -EC version) tapped mounting holes with a 0.2 mounting depth and includes a switchable line voltage power supply. The desired tube control voltage has to be kept in the range of 0 to 1.25V. The anode current should not $100\mu\text{A}$. The anode current is dependent on both the sensitivity of the PMT at a given wavelength and the applied voltage. The maximum output of the PMM01 is 10V for high impedance loads (5V for 50Ω loads). The output signal should be below the maximum output voltage to avoid saturation. If necessary, use external neutral density filters to reduce the input light level. A class 3B laser was used for this experiment. To have the laser at a fixed point on the rotating arm of the spectrometer a laser arm was pre-designed and constructed. An optical chopper was placed in front of the laser and before the Eco-brick being tested. This was held in place by a retort stand and used to modulate the laser beam at a frequency of approximately 1kHz. Once the set-up was turned on, a laser beam is emitted towards the test subject, the PMT then detects any beams that have passed through the brick and the results can be taken from a multimeter. The results should be considered for a number of angles. These angles can be made by rotating the arm with the PMT attached to it and the angle can be read from the vernier scale on the

1 spectrometer. While undertaking the experiment it is pivotal to ensure that the experiment
2 is done in dark surroundings. Any form of daylight entering the room where the tests are
3 carried out can hinder the results received by the apparatus. The protective black boards
4 that are put up around the apparatus are to prevent any deflected beams that might refract
5 away. This prevents any rays that might refract towards a person within the vicinity of the
6 experiment.

7

8 **5. Results**

9 **5.1 Compression Testing**

10 The bottle weights, brick weights and compressive loads at failure as defined in the
11 previous section, are presented in Table 1 for 10 Eco-bricks tested.

12 All of the initial bottle weights are very similar, within a range of 24 to 27 grams. As the
13 bottles are all the same size, the similar weights of each give an indication that that all
14 bottles are made from a similar standard of plastic, and that this would have equal on the
15 compressive force. All final manufactured Eco-bricks have a similar weight, the lowest
16 being 245 grams up to 260 grams. The bricks themselves showed good resistance to the
17 compressive force applied; displaying values of up to 40 kN, these values are similar to
18 that of basic concrete cubes that are tested using the same machine and process. There
19 appears a linear relationship between the weight of a brick and the compressive force it
20 can bear, though they are not directly related. This is shown in Figure 4. Since all bottles
21 are made from a similar grade of plastic, this means that the packing ratio is the main
22 variable that affects the strength of the brick.

23

1 To obtain an estimated stress at failure, the area of the squashed specimen is found by
2 tracing the outline of the bottle onto a piece of paper and drawing a series of rectangles
3 and trapezoids, calculating the area of each and adding them all together. The stress at
4 failure, indicative of its compressive strength, was assessed by dividing the force at
5 failure divided by this area. Table 2 presents the computed results in this regard. The
6 manufacturing of the PET bottles and the failures are consistent to the resolution to which
7 the results have been reported.

8 The specific strength of a material may be represented through the strength/weight ratio.
9 It is computed by dividing estimated strength with bulk mass per unit volume. For
10 calculating bulk mass per unit volume, the mass of the bottle is divided by the volume. It
11 can be assumed that the volume of each brick is the same as they are all 500 ml bottles.
12 Their volume, in reality, may slightly vary but this is negligible when a first estimate of
13 strength of Eco-bricks is being made. Table 3 presents the specific strengths of the Eco-
14 bricks.

15 The linear relationship between specific strength and weight is presented in Figure 5.

16 When the specimen is squashed to a contraction in the direction of the applied load, there
17 is a corresponding extension in a direction perpendicular to the applied load. The ratio
18 between these two quantities is estimated as the Poisson's ratio. The Poisson's ratio was
19 calculated by comparing the axial and transverse strain at failure. The brick displays slight
20 elastic rebound as it regains some of its shape when loading is removed. To measure axial
21 strain the distance between the two platens is measured upon failure, and then divided by
22 its original length. The extension and contraction is measured about the centre of the
23 brick. The Poisson's ratios for the Eco-bricks were estimated within a range of 0.27-0.35.

1 5.2 Sound Insulation

2 Sound reduction index (R) of Eco-bricks were estimated using the Mass Law, The
3 reduction in dB at normal incidence,

$$4 R_o = 20 \log \left(\frac{\omega m}{2 \rho c} \right) \quad (1)$$

5 where $\omega = 2\pi f$ is the angular velocity of the sound in radians/s, m is the mass of the
6 partition per unit area in kg/m^2 and ρc is the characteristic acoustic impedance of air in
7 Rayls ($\frac{\text{Pa}\cdot\text{s}}{\text{m}}$), which is about $420 \frac{\text{Pa}\cdot\text{s}}{\text{m}}$ at room temperature.

8 Reduction in dB for all angles of incidence is expressed as

$$9 R = R_o - 10 \log(0.23R_o) \quad (2)$$

10 A comparison of sound reduction index with Eco-bricks and other traditional
11 construction materials are presented in Figure 6.

12 Eco-bricks do not have as good a sound reduction index as a concrete block. However,
13 the lack of performance is not too significant. Additionally, with the addition of mortar to
14 the walls made from bottle “eco-bricks” this would increase the sound reduction index of
15 the walls thus increasing the overall sound insulation of the structure being constructed.

16 An alternative option of the bottle Eco-brick filled with sand was also assessed for sound
17 reduction index. This is better than the plastic version but still not as good as the concrete
18 block and the use of sand defeats the purpose of removing waste plastic from the system.

19 A 110 dB sound between 1000 and 5000Hz, centred at around 3500Hz, is a value that is
20 close to the threshold of pain to the ear [32]. With a sound reduction index of roughly 44
21 dB, the bottle eco brick alone can reduce the figure of this sound down to around 70dB
22 which is the same value as a normal conversation would be at. This would be even

1 further reduced by mortar, if it is used. Sound insulation is heavily dependent on the
2 quality of construction and workmanship.

3

4 **5.3 Light Transmission**

5 The range was turned down on the lock-in amplifier to 300nV, without seeing any signal
6 from the PMT. It can thus be said that the signal out from the lock-in is < 300nV.

7 The PMT produces a current, rather than a voltage as its output. It is converted to voltage
8 by a factor of 10^6VA^{-1} passing through a $1\text{M}\Omega$ resistor. The current from the PMT (I_{PMT})
9 is

$$10 \quad I_{PMT} < \frac{300 \times 10^{-9} \text{V}}{10^6 \text{V/A}} = 300 \times 10^{-15} \text{A} \quad (3)$$

11 The PMT has a sensitivity of 86 V/W. Consequently, the optical power incident on the
12 PMT is

$$13 \quad P_{opt} < \frac{300 \times 10^{-15} \text{A}}{86 \text{A/W}} = 3.5 \times 10^{-15} \text{W} \quad (4)$$

14 The transmission (T) of the sample is the proportion of the incident light that would pass
15 through the specimen. This is obtained by

$$16 \quad T < \frac{3.5 \times 10^{-15} \text{W}}{4.5 \times 10^{-1} \text{W}} = 8 \times 10^{-13} \quad (5)$$

17 As the above result is a ratio, it can also be expressed as < 120dB. This means that there
18 is minimal transmission of light passing through the brick. The amount of light is so
19 minimal that it is not visible to the human eye but it is picked up by the apparatus.

20

21 **6. Discussion**

1 A major motivation behind carrying out the work was the immediate applicability of Eco-
2 bricks in various situations. The lead author has already been a part of a volunteering
3 project in Costa Rica introducing Eco-bricks as a building resource. There was an
4 existing problem with plastic waste related to protective covering for berry farming that
5 was addressed through Eco-bricks.

6 Using concrete blocks instead of Eco-bricks has its advantages and disadvantages. The
7 cost of Eco-bricks is zero whereas the cost of a block in Central America for example
8 averages out at roughly 75c per block. Considering a small, three room Eco-brick house
9 for four people, made of 8000 Eco-bricks, there is a potential saving around €1500. On
10 the other hand, the use of concrete blocks requires significantly less labour. The issue
11 with the cost of the Eco-bricks is deciding to hire labour. Usually, it takes 30 to 60
12 minutes to make one brick and the main deciding factor for practical implementation will
13 be labour.

14 There are potential applications of Eco-bricks in basic constructions. They can also be
15 used for decorative purposes for community areas such as parks. Other possible potential
16 applications may include assessing the efficacy of Eco-bricks in stabilising soil, slopes or
17 being used as barriers.

18 Ecological approaches towards the development of units of construction is gaining
19 increasing popularity for cleaner production processes in geographical regions where
20 which are already experiencing or are expected to experience significant anthropogenic
21 pollution levels due to rapid industrialisation [33]. The use of PET bottles as an additive
22 for construction units have been considered before [34-36]. On the other hand, novel
23 ideas of producing ecological bricks is also known to researchers [37-39]. This first

1 approach of creating a structural unit entirely from PET bottles filled with plastic bags,
2 which is expected to a unique and interesting way of recycling these materials with
3 potential applications in construction.

4

5 **7. Conclusions**

6 It can be concluded that Eco-brick is a viable resource for construction purposes with a
7 number of possible applications. The bricks are relatively easily manufactured with
8 controlled weight and packing. Eco-bricks have relatively good compressive strength,
9 with values matching that of basic concrete cubes. The weight of Eco-brick was observed
10 to hold a nearly relationship with load at failure and with specific strength. Eco-bricks
11 have a relatively good specific strength. They are lightweight but strong for the weight
12 they bear. The lightweight properties of the brick would reduce the cost of transportation
13 if necessary. The calculated Poisson's ratio was observed to be within the range of 0.27
14 to 0.35. Eco-bricks have a relatively high sound reduction index, even when compared to
15 that of a normal concrete block, which is a far more dense material. It has been shown
16 that light visible to the naaked eye does not appear to travel through Eco-bricks.
17 Lightweight Eco-bricks also reduce the chances of injury due to lifting heavy materials.
18 The bricks are non-brittle, unlike concrete blocks. They are a simple recycling
19 advancement, reaping significant environmental benefits. They save on trash travel
20 allowance and landfill space. There is one inconvenient negative aspect of the brick and
21 that is their fire resistance. Plastic can be set alight quite easily but considering that they
22 are covered by a cement/sand mix or mud this will aid in the lack of fire resistance from
23 the bricks themselves.

1

2 **Acknowledgements**

3 The authors are grateful to Mr. Anthony O’Flaherty, Department of Civil and
4 Environmental Engineering, University College Cork; Lawrence Singleton, Adrian James
5 Acoustics; Dr. Richard Green, Department of Physics, University College Cork and
6 Jonathan Cerdas, Santos Tours, Costa Rica.

7 The authors also acknowledge Engineers Without Borders: Ireland for this work.

8

9

References

1. Shent, H., Pugh, R.J., Forssberg, E., 1998, A review of plastics waste recycling and the flotation of plastics. *Resources, Conservation and Recycling* 25, 85–109.
2. Subramanian, P.M., 2000. Plastics recycling and waste management in the US. *Resources, Conservation and Recycling*. 28, 253–263.
3. Mutha, N.H., Martin Patel, M., Premnath, V., 2006. Plastics materials flow analysis for India. *Resources, Conservation and Recycling* 47, 222–244.
4. Pacheco, E.B., Luiza M. Ronchetti, L.M., Masanet, E., 2012. An overview of plastic recycling in Rio de Janeiro. *Resources, Conservation and Recycling* 60, 140– 146.
5. Carvalho, M.T., Agante, E., Duraõ, F., 2007. Recovery of PET from packaging plastics mixtures by wet shaking table. *Waste Management* 27, 1747–1754.
6. Al-Salem, S.M., Lettieri, P., Baeyens, J., 2009. Recycling and recovery routes of plastic solid waste (PSW): A review. *Waste Management* 29, 2625–2643.
7. O’Brine, T., & Thompson, R. C., 2010. Degradation of Plastic Carrier Bags in the Marine Environment. *Marine Pollution Bulletin*, 2279–2283.
8. EU, 2008. Directive 2008/98/EC of the European parliament and of the council of 19 November 2008 on waste and repealing certain directives.
9. Muthu, S., Li, Y., Hu, J., & Mok, P, 2011. Carbon footprint of shopping (grocery) bags in China, Hong Kong and India. *Atmospheric Environment*. 45, 469-475.
10. Lajeunesse, S., 2004. Plastic bags. *Chemical and Engineering News*. In S. Lajeunesse, *An Overview of Carryout bags in Los Angeles County*. Los Angeles: Los Angeles County Department.
11. Dilli, R., 2007. Comparison of existing life cycle analysis of shopping bag alternatives. Final Report for Sustainability Victoria. Hyder Consulting Pty Ltd., Melbourne, Victoria.
12. SETAC., 1993. Guidelines for Life Cycle Assessment. Sesimbra, Portugal, Brussels, Belgium, Pensacola, Florida: First Ed, SETAC Workshop.
13. ISO 14040. Environmental management. Life cycle assessment. Principles and framework; 1997.
14. Lazarevica, D., Aoustin, E., Buclet, N., Brandt, N., 2010. Plastic waste management in the context of a European recycling society: Comparing results and uncertainties in a life cycle perspective. *Resources, Conservation and Recycling* 55, 246–259.
15. Department of Environment, 2007. Plastic Bags. from Department of Environment, Community and Local Government : <http://www.environ.ie/en/Environment/Waste/PlasticBags/> (Date of access 14/03/2014)
16. Siddique, R., Khatib, J., Kaur, I., 2008. Use of recycled plastic in concrete: A review. *Waste Management* 28, 1835–1852.
17. Hannawi, K., Kamali-Bernard, S., Prince, W., 2010. Physical and mechanical properties of mortars containing PET and PC waste aggregates. *Waste Management* 30, 2312–2320.
18. Choi, N. W., Mori, I. Ohama, Y., 2006. Development of rice husks–plastics composites for building materials. *Waste Management* 26, 189–194.
19. Marzouk, O.Y., Dheilly, R.M., Queneudec, M., 2007. Valorization of post-consumer waste plastic in cementitious concrete composites. *Waste Management* 27,

310–318.

20. Frigione, M., 2010. Recycling of PET bottles as fine aggregate in concrete. *Waste Management* 30, 1101–1106.
21. Akcaozog˘lu, S., Atis, C.D., Akcaozog˘lu, K., 2010. An investigation on the use of shredded waste PET bottles as aggregate in lightweight concrete. *Waste Management* 30 (2), 285–290.
22. Ismail, Z.Z., AL-Hashmi, E.A., 2008. Use of waste plastic in concrete mixture as aggregate replacement. *Waste Management* 28, 2041–2047.
23. Albano, C., Camacho, N., Hernandez, M., Matheus, A., Gutierrez, A., 2009. Influence of content and particle size of waste pet bottles on concrete behavior at different w/c ratios. *Waste Management* 29, 2707–2716.
24. Sivakumar Babu, G.L., Chouksey, S.K., 2011. Stress–strain response of plastic waste mixed soil. *Waste Management* 31, 481–488.
25. POLLI-Brick. (2011). Polli-brick. <http://www.miniwiz.com/miniwiz/en/products/living/polli-brick>. (Date of access 14/03/2014)
26. Hopkins, C., 2007. *Sound Insulation*. Elsevier Ltd.
27. Smith S. W., 2003. *Digital Signal Processing, A Practical Guide for Engineer's and Scientists*; Newnes Publications Ltd.
28. Griffiths, D. J. (2004). *Introduction to Quantum Mechanics (2nd ed.)*. Prentice Hall.
29. Cassidy, N., Eddies, R., Dods, S., 2011. Void detection beneath reinforced concrete sections: the practical application of ground-penetrating radar and ultrasonic techniques. *Journal of Applied Geophysics* 74(4), 263-276.
30. Nelligan, T., 2012. *Ultrasonic Flaw Detection*. <http://www.olympus-ims.com/en/applications-and-solutions/introductory-ultrasonics/introduction-flaw-detection>. (Date of access 14/03/2014)
31. Building Regulations, T., 2010. Resistance to the Passage of Sound, Document E. In H. Government, *The Building Regulations*. NBS, RIBA Enterprises Ltd.
32. NetWell Noise Control. 2012. Decibel Chart from NetWell Noise Control: <http://www.controlnoise.com/decibel-chart>. (Date of access 14/03/2014)
33. Rahman M.E., Muntohar A.S., Pakrashi, V., Nagaratnam, B.H., Debnath S., 2014. Self Compacting Concrete from Uncontrolled Burning of Rice Husk & Blended Fine Aggregate. *Materials & Design*, 55, 410-415
34. Ahmadinia E., Zargar ., Karim M.R., Abdelaziz M., Shafiq P., 2011. Using waste plastic bottles as additive for stone mastic asphalt. *Materials & Design*, 32(10), 4844-4849.
35. Tan C., Ahmad, I., Heng M., 2011. Characterization of polyester composites from recycled polyethylene terephthalate reinforced with empty fruit bunch. *Materials & Design*, 32 (8–9), 4493-4501.
36. Iucolano F., Liguori B., Caputo D., Colangelo F., Cioffi R., 2013. Recycled plastic aggregate in mortars composition: Effect on physical and mechanical properties. *Materials & Design*, 52, 916–922.
37. Maskell D., Heath A., Walker P., (2013). Laboratory scale testing of extruded earth masonry units. *Materials & Design*, 45, 359–364.

38. Grist E.R., Paine K.A., Heath A., Norman J., Pinder H., 2013. Compressive strength development of binary and ternary lime–pozzolan mortars. *Materials & Design*, 52, 514–523.
39. Hajjaji W., Andrejkovičová S., Zanelli C., Alshaaer M., Dondi M., Labrincha J.A., Rocha F., 2013. Composition and technological properties of geopolymers based on metakaolin and red mud. *Materials & Design*, 52, 648–654.

List of Figures

Figure 1. An example of an Eco-brick.

Figure 2. Development of Eco-bricks through collection of PET bottles (a) PET bottle (b), collection of waste plastic (c), packing of waste plastic within PET bottles (d) and closing PET bottles with a screw cap

Figure 3. Conversion of circular to a trapezoidal shape for different sections.

Figure 4. Linear relationship between Eco-brick weight and compressive force at failure.

Figure 5. Linear relationship between Eco-brick weight and specific strength.

Figure 6. A comparison of sound reduction indices for Eco-bricks and other traditional bricks used for construction.



Figure 1.



Figure 2.

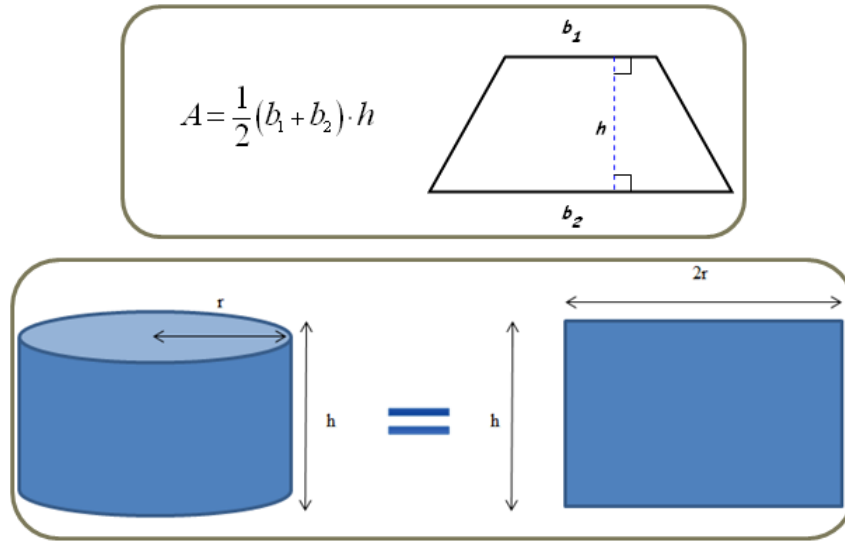


Figure 3.

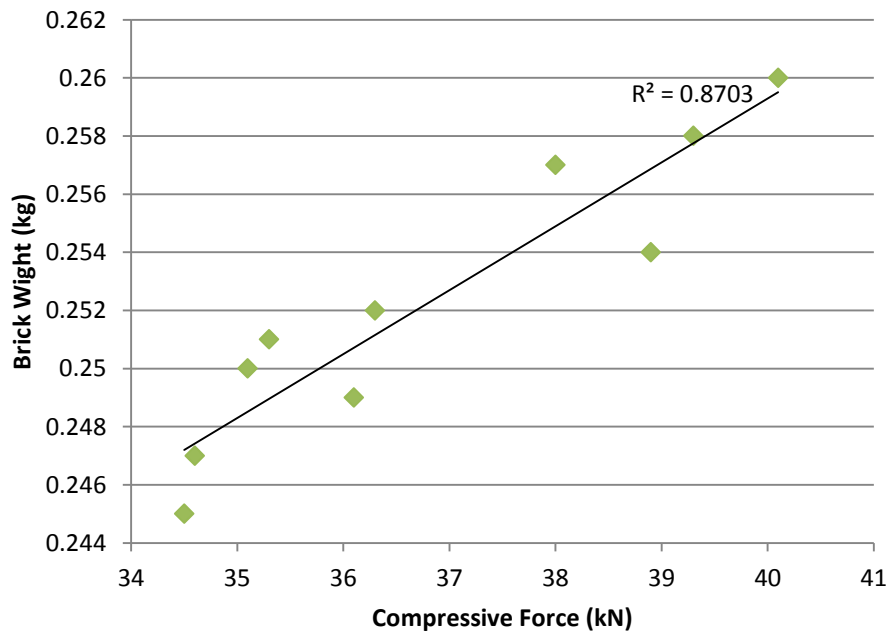


Figure 4.

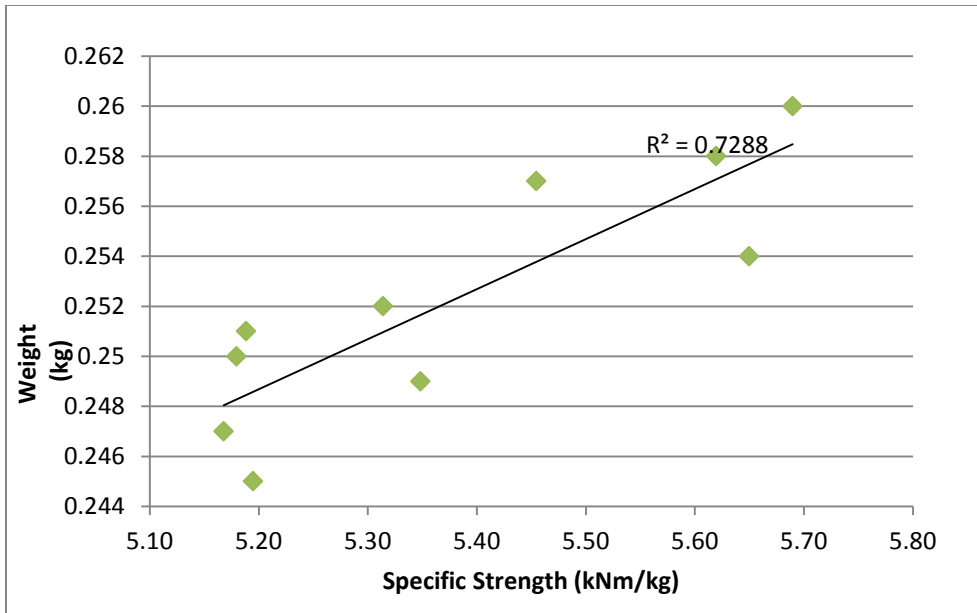


Figure 5.

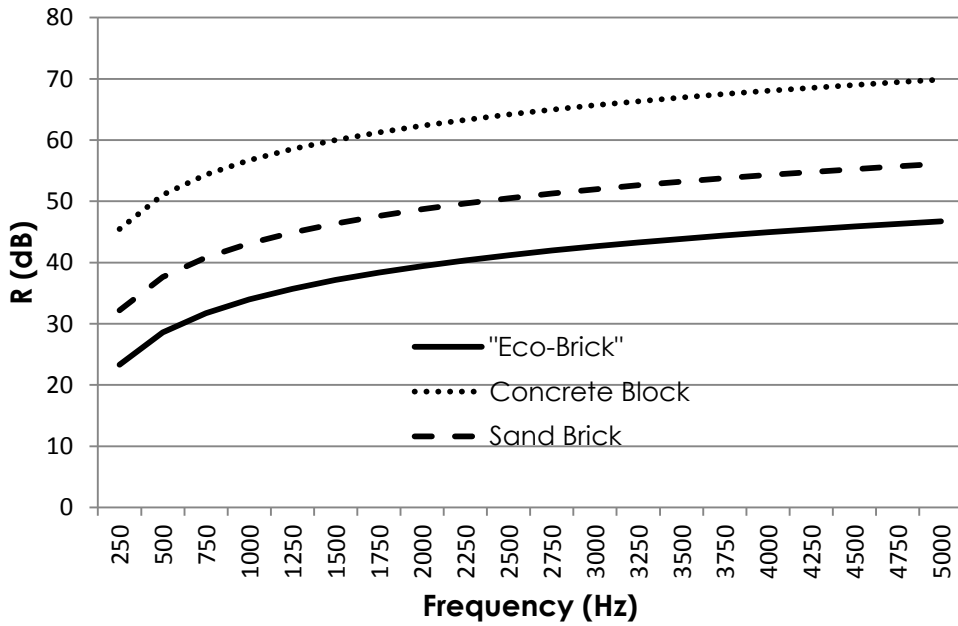


Figure 6.

List of Tables

Table 1. Compressive loads at failure along with bottle and brick weights.

Table 2. Estimated compressive strength at failure.

Table 3. Specific strengths of Eco-bricks.

	Bottle Weight (g)	Brick Weight (g)	Compressive Force (kN)
Specimen 1	26	250	35.1
Specimen 2	25	247	34.6
Specimen 3	26	258	39.3
Specimen 4	27	260	40.1
Specimen 5	25	251	35.3
Specimen 6	27	254	38.9
Specimen 7	24	245	34.5
Specimen 8	26	249	36.1
Specimen 9	25	252	36.3
Specimen 10	25	257	38.0

Table 1.

	Compressive Force (kN)	Area (m²)	Strength (MPa)
Specimen 1	35.1	0.0136	2.59
Specimen 2	34.6	0.0136	2.55
Specimen 3	39.3	0.0136	2.90
Specimen 4	40.1	0.0136	2.96
Specimen 5	35.3	0.0136	2.60
Specimen 6	38.9	0.0136	2.87
Specimen 7	34.5	0.0136	2.55
Specimen 8	36.1	0.0136	2.66
Specimen 9	36.3	0.0136	2.68
Specimen 10	38.0	0.0136	2.80

Table 2.

	Pressure (MPa)	Bulk Mass per Unit Volume (kg/m³)	Specific Strength (kNm/kg)
Specimen 1	2.59	500	5.18
Specimen 2	2.55	494	5.17
Specimen 3	2.90	516	5.62
Specimen 4	2.96	520	5.69
Specimen 5	2.60	502	5.19
Specimen 6	2.87	508	5.65
Specimen 7	2.55	490	5.20
Specimen 8	2.66	498	5.35
Specimen 9	2.68	504	5.31
Specimen 10	2.80	514	5.45

Table 3.